

LiBC - A prevented superconductor

B. Renker,¹ H. Schober,² P. Adelman,¹ P. Schweiss,¹ K.-P. Bohnen,¹ and R. Heid¹

¹*Forschungszentrum Karlsruhe, IFP, P.O.B. 3640, D-76021 Karlsruhe, Germany and*

²*Institut Laue-Langevin, BP 156 X, F-38042 Grenoble Cedex, France*

(Dated: February 6, 2008)

We have investigated the lattice dynamics of LiBC. Experimental Raman and inelastic neutron scattering results are confronted with density functional calculations. The excellent agreement between experiment and theory indicates that we have attained a high level of understanding for LiBC, which by its structure is closely related to superconducting MgB₂. We will show that annealing of the sample is insufficient to cause Li deficiency and thus produce the expected superconductivity.

PACS numbers: 74.25.kc, 63.20.kr, 78.70.Nx, 71.20.Lp

The simple binary compound MgB₂ has attracted considerable attention because of its exceptional superconducting properties. A strong coupling of the electronic system to high-frequency boron in-plane phonon modes meets the BCS requirements for a transition temperature as high as 40 K [1, 2]. A most prominent experimental manifestation of this coupling is the extreme broadening of the E_{2g} mode in the Raman spectrum [2, 3]. Very recently theoretical speculations of transition temperatures as high as 120 K i.e. largely exceeding those of MgB₂, have been published for LiBC compounds with Li deficiencies in the range of 25 % [4]. With respect to structural peculiarities LiBC provides a comparable system to MgB₂. B and C atoms alternately occupy the sites within the hexagonal sheets. Charge neutrality is restored by replacing Mg⁺² by Li⁺. A doubling of the unit cell along the hexagonal axis occurs due to an interchange of B and C atom positions in neighboring planes[5]. So far no convincing experimental evidence for superconductivity could be established [6, 7]. In this context, it is most interesting to investigate the lattice dynamics of this particular compound and to compare it with our previous results for MgB₂ and AlB₂.

LiBC has been synthesized following a procedure which is described in detail in Ref. [5]. In view of our neutron scattering experiments we have used isotope pure ⁷Li metal together with amorphous ¹¹B and graphite powders. The mixed components were pressed into pellets and held in a closed Nb tube at 1500°C for 3 h. The final product was homogeneous and consisted of yellow shining crystallites with clean faces and metallic brightness. Stoichiometric LiBC has been shown to be semiconducting and to belong to the space group P6₃/mmc which was also confirmed by our own *x*-ray refinements. Hexagonal shaped platelets with diameters of up to 200 μm and 20 μm in thickness could be found and were chosen for optical measurements. All of our samples - the as prepared, the annealed and the Na doped ones - proved to be non-superconducting above 4 K. For inelastic neutron measurements the microcrystalline powders were filled into flat pockets of 2 × 3 × 0.3 cm³ made from Al-foil. Measurements were performed at 300 K on the time-of-flight spectrometers IN6 (incoming energy 4.7 meV) and IN4 (incoming energy 39.4 meV) at the HFR in Greno-

ble (France) in the upscattering mode. A generalized phonon density of states (GDOS) was obtained from the sum of scattering spectra recorded over a large angular range from 10° to about 120°. The IN6 and IN4 GDOS coincide well above 10 meV indicating that the incoherent approximation works very well. Only small coherence effects are observed in the IN6 data below 10 meV due to the fact that the *Q*-space is less extensively sampled with the longer wavelength neutrons at these small energy transfers. Multi-phonon contributions were removed via a self-consistent calculation procedure.

The factor group analysis yields 2A_{2u} + 2B_{1g} + B_{2u} + 2E_{1u} + 2E_{2g} + E_u zone center optic modes where only the 2E_{2g} modes are Raman (R) active. The latter modes should be observable for all configurations with polarization vectors of the incoming and the reflected light within the hexagonal plane. Zero intensity is expected if one of these vectors is parallel to the crystallographic *c* axis. The spectra shown in Fig. 1 prove that this is essentially the case. In particular we do not observe additional strong and sharp lines at 546 cm⁻¹ and 830 cm⁻¹ which have been reported by other authors [8] and which have been taken as a reason to propose the lower symmetric space group *P* $\bar{3}$ m1 for LiBC. These authors conclude on a particular “puckering” of hexagonal B-C planes. We have never observed these lines although we have noticed that the background spectrum may depend on details of the sample preparation. A high Li vapor pressure at the synthesis temperature around 1500°C and possible small leaks in the container may cause problems in sample preparation. However, a broader contribution around 1270 cm⁻¹ is also observed in our polarized spectra. It is not allowed as a one phonon contribution. Its intensity when compared to the allowed line at 1168 cm⁻¹ is sample dependent and gets weaker on cooling. It is attributed to second order scattering or to structural defects although its origin is not fully understood.

The important hole doping of B 2*p* – *σ* bands in MgB₂ is caused by the relative shift of *π* and *σ* bands in this particular compound. This does not occur for LiBC. However, there are speculations that a doping could be achieved by Li deficiency. We have annealed samples at 800°C, 1000°C and 1200°C for ≥ 3 h in dynamic vacuum in order to reduce the Li content. Structural changes

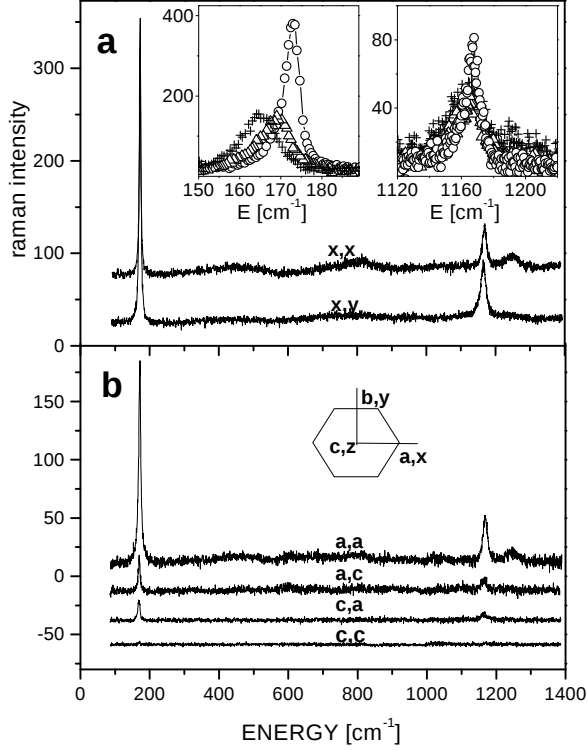


FIG. 1: Observed Raman signals from a LiBC single crystal in backscattering configuration. a: scattering from the hexagonal plane, the small contribution near 1240 cm^{-1} in the polarized spectrum is not allowed for $P6_3/mmc$ symmetry. Results for the treated materials are shown by inserts: open circles - as prepared, triangles - annealed at 1000°C , crosses - $\text{Li}_{0.95}\text{Na}_{0.05}\text{BC}$, b: scattering from an ac-plane: the lettering above the spectra marks the polarization vectors of the incoming and outgoing light. In agreement to the selection rules strong Raman signals are only observed if both polarization vectors are contained within the hexagonal plane.

within the Li sheets which provide a coupling between neighboring B-C planes are expected to show up in the sliding frequency at 171 cm^{-1} (see Tab. 1). However, little changes are observed in the R-spectra up to annealing temperatures of about 800°C when Li starts to evaporate. For the sample which was annealed at 1000 K we observe a small but significant downshift of the sliding frequency indicating a possible decrease in the Li concentration. A somewhat larger shift was observed for a sample of nominal $\text{Li}_{0.95}\text{Na}_{0.05}\text{BC}$. For the B-C stretching mode at 1167 cm^{-1} we register a still smaller relative shift which let us conclude that the obtained changes in the electronic system are negligible. These results were reproducible on different crystallites and are shown in detail by the inserts in Fig. 1. Thus neither the proposed dramatic softening nor any significant line broadening as observed for MgB_2 occur. In view of the high frequency of the E_{2g} in-plane mode LiBC resembles much more the compound AlB_2 . Indications of sample disintegration, i.e. a decrease in intensity of the two E_{2g} lines and broader contributions

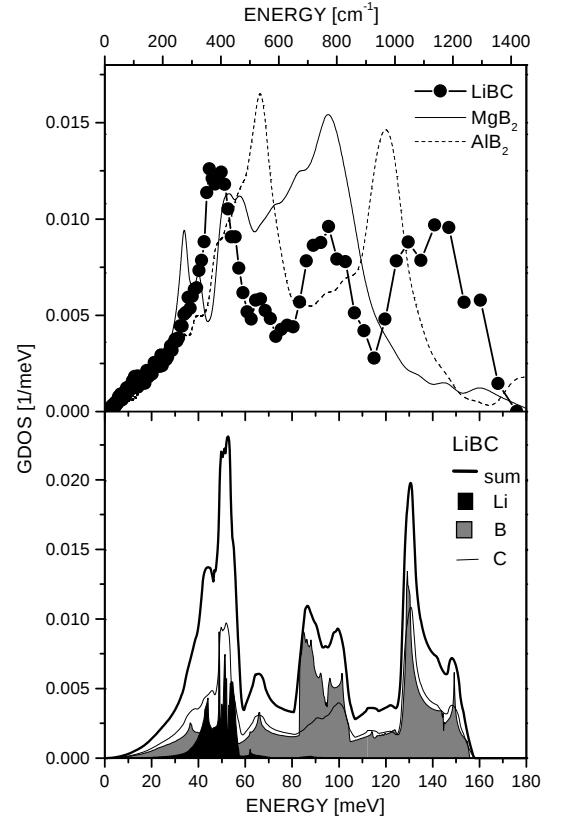


FIG. 2: Experimental generalized phonon density of states for as prepared LiBC, superconducting MgB_2 and non-superconducting AlB_2 (the latter two spectra are results from preceding measurements [3] under the same conditions). A pronounced down-shift and broadening of the high energy peak visible for MgB_2 is absent for LiBC. LiBC resembles much more AlB_2 . Lower frame: Theoretical results for stoichiometric LiBC proving the high quality of calculations based on density functional theory. Results for the partial DOS are helpful for a more detailed interpretation of the experimental spectrum.

at energies $> 1200\text{ cm}^{-1}$, are observed for samples with annealing temperatures $> 1370\text{ K}$. Since samples which already start to show signatures of disintegration in the R-spectrum still exhibit the correct x -ray structure it is concluded that disintegration starts on the surface of the crystallites.

Augmenting results are obtained by inelastic neutron scattering which can access all excitations in the entire zone and which investigates the whole volume of the crystallites. In Fig. 2 we show the generalized phonon density-of-states measured at 300 K . The spectrum consists of three main peaks. Hard B and C in-plane and out-of-plane modes are grouped around 150 meV and 100 meV respectively. Modes where neighboring B-C sheets slide against each other as well as vibrations of the weaker bond Li-ions contribute to the lowest peak around 50 meV . Fig. 1 shows that the upper two peaks in LiBC group around the corresponding line of AlB_2 which reflects the doubling of the unit cell in c direction

. A shoulder around 160 meV agrees well to the “forbidden” line at 1270 cm^{-1} in the R-spectrum. A clear result is that the significant down-shift and broadening of the high energy peak of MgB_2 does not occur for our sample of as prepared LiBC. Therefore, the spectrum of undoped LiBC resembles much more the GDOS of AlB_2 . The exceptional behaviour of MgB_2 is besides structural differences the result of strong electron-phonon coupling for the E_{2g} mode (1167 cm^{-1} for LiBC). Here, both experiments agree that nothing comparable exists for the as prepared sample of LiBC. A hybridization of Li modes with the underlying B(C) partial DOS is however also registered in the GDOS spectra of LiBC.

A crucial question is, whether it is possible to obtain a sufficiently strong doping of LiBC by Li evaporation. In Ref.[5] the authors were confident that this could be achieved. For superconductivity it would be important to obtain a homogeneous doping of the entire material without damage of the main structure. This however could not be observed in our R-spectra which investigate the surface of the crystallites. With INS we can see the whole volume. In Fig.3 we show GDOS spectra which have been obtained for samples with different annealing temperatures. It can be seen clearly that no shift in the peak positions occurs. Up to $\approx 1120\text{ K}$ the sample seems stable. Annealing at still higher temperatures damages the whole sample. The initially sharp peaks start to disappear remarkably without any significant shifts in their position. A hump around 20 meV rises up and signalizes the formation of amorphous material. This spectral change is still more pronounced in the original time-of-flight spectra. It is a clear result of our measurements that not enough of the Li ions sandwiched between the hexagonal B,C-planes can be removed in order to cause the desired changes in the electronic system. Dramatic changes due to an unusually strong electron-phonon coupling even more pronounced than those found for MgB_2 otherwise should have been observed.

A detailed analysis of our experimental data has been performed by calculations based on density functional theory. This technique provides an accurate and parameter free analysis of the electronic structure and the bonding properties. Our calculations which correspond to those performed for other diborides [2, 9] are based on a perturbational approach using the mixed basis pseudopotential method and provide information on the phonon frequencies and electron-phonon coupling within the whole BZ. Pseudopotentials for Li and C [11] were constructed according to Hamann-Schlüter-Chiang whereas for B a Vanderbilt-type potential was chosen. Our calculations apply to stoichiometric LiBC and the structure $\text{P6}_3/\text{mmc}$ which assumes a regular stacking of hexagonal B-C planes and sheets of Li ions sitting on the corner of trigonal prisms. It can be seen from Fig. 2 that a very high level of correspondence to the experimental GDOS is reached. All distinct maxima correspond to similar features in the experimental spectrum. The very high frequency shoulder at 160 meV is not part of the cal-

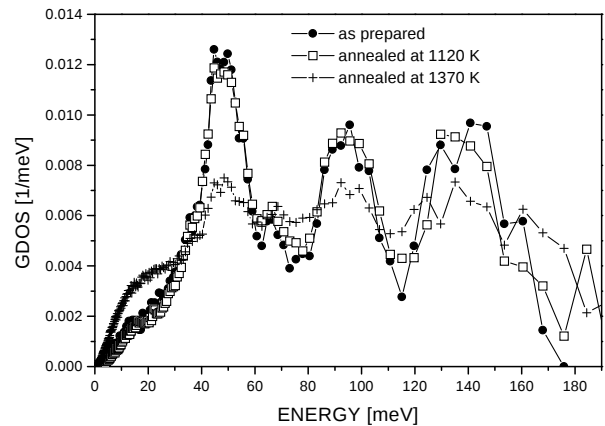


FIG. 3: Measured GDOS spectra for LiBC samples which were annealed for 3 h in dynamic vacuum at the indicated temperatures in order to obtain a hole doping of B-C layers due to Li deficiency. Changes in the electronic system are believed to manifest in distinct peak shifts which are not observed even if the sample starts to disintegrate.

TABLE I: Calculated Γ point frequencies in meV (cm^{-1})

sym	ω	elongations
E_{2g}	21.8	E_{2g} , B-C planes slide against each other
(R)	(176)	
E_{2u}	37.3	Li layers slide against each other
	(301)	
B_{1g}	39.5	symmetric vibration of B-C layers
	(319)	
E_{1u}	43.9 (T)	Li layers slide against B-C layers
(IR)	(354)	
	47.4 (L)	
	(382)	
A_{2u}	56.7 (T)	Li layers vibrate against B-C layers
(IR)	(457)	
	69.9 (L)	along c
	(563)	
B_{2u}	67.9	Li layers vibrate against each other
	(548)	
A_{2u}	101.5 (T)	B and C layers move against each other
(IR)	(819)	
	104.2 (L)	along c, Li not at rest
	(840)	
B_{1g}	104.5	symmetric vibration of B-C layers
	(843)	
E_{1u}	140.9 (T)	B-C bond stretching mode odd
(IR)	(1136)	
	152.7 (L)	displacement of B-C layers
	(1231)	
E_{2g}	142.0	B-C bond stretching mode even
(R)	(1145)	
		displacement of B-C layers in phase

culated spectrum which suggests an interpretation as a defect induced contribution. Furthermore it can be seen from the partial DOS that the Li modes overlap with B and C vibrations. Thus a scenario similar to MgB_2 seems possible for samples with sufficiently high doping. A significant feature of a very strong electron-phonon

coupling in MgB_2 was the drop of the E_{2g} in-plane mode at Γ well below the B_{1g} out-of-plane mode. In Tab.1 we have listed all calculated Γ -point frequencies ordered according to increasing energies. For the IR-active modes the LO (L) and TO (T) splitting has been calculated. A good correspondence to the measured R-lines is registered. Again with respect to the position of the E_{2g} and B_{1g} modes it can be seen that stoichiometric LiBC is far away from the favourable situation found in MgB_2 .

In conclusion, it is a success that larger single crystalline specimens of LiBC with the shape of beautiful hexagonal prisms can be prepared. We register that the R-selection rules are fully obeyed for our samples. A small hump near 1270 cm^{-1} in the (x,x)-spectrum probably originates from disorder. There is no x -ray evidence of any second phase in the investigated single crystals.

Any significant doping by an evaporation of Li in dynamic vacuum was not possible for the investigated single crystals although very small frequency shifts occur for the sliding mode at 171 cm^{-1} . It is also a clear result that in our preparation crystallites with a “puckering” of the hexagonal B-C planes were not obtained.

The generalized phonon density of states (GDOS) has been measured by INS and proves the very high quality of first principals calculations. The experimental spectrum of the undoped compound resembles much more that of AlB_2 than MgB_2 , i.e. signatures of any stronger electron-phonon coupling are fully absent for LiBC.

The preparation of doped LiBC crystals still remains a challenge for sample preparation. Simple annealing in dynamic vacuum however will cause a disintegration of LiBC crystals as demonstrated in these investigations.

-
- [1] J. Kortus, I. I. Mazin, K. D. Belashenko, V. P. Antropov, and L. L. Boyer, Phys. Rev. Lett. **86**, 4656 (2001)
 - [2] K.-P. Bohnen, R. Heid, and B. Renker, Phys. Rev. Lett. **86**, 5771 (2001)
 - [3] B. Renker, K.-P. Bohnen, R. Heid, D. Ernst, H. Schober, K. Koza, P. Adelman, P. Schweiss, and T. Wolf, Phys. Rev. Lett. **88**, 067001 (2002)
 - [4] H. Rosner, A. Kitaigorodsky, and W.E. Pickett, Rev. Lett. **88**, 127001 (2002)
 - [5] M. Wörle, R. Nesper, G. Mair, M. Schwarz, and H. G. Schnering, Z. Anorg. Allg. Chem., **621**, 1153 (1995)
 - [6] A. Bharathi, S.J. Balaseli, M. Premila, T.N. Sairam, G.L.N. Reddy, C.S. Sundar, and Y. Hariharan, cond-mat 0207448 **591**, 594 (2002)
 - [7] D. Souptel, Z. Hassain, G. Behr, W. Löser, Ch. Geibel, cond-mat 0208346 **329**, 311 (2002)
 - [8] J. Hlinka, I. Gregora, A.V. Pronin, and A. Loidl cond-mat/0207683 (2002)
 - [9] R. Heid, K.-P. Pohnen, and B. Renker, Adv. in Solid State Phys. **42**, 293 (2002)
 - [10] J.M. An, H. Rosner, S.Y. Savrasov, and W.E. Pickett, cond-mat/0209256 (2002)
 - [11] K.-P. Bohnen, R. Heid, K.-M. Ho, and C. T. Chan, Phys. Rev. B **51**, 5805 (1995)